

Sent to me on 10/15/86

to Rick Goene

H. Alex Maten.

Susceptibility Measurements Support High T_c Superconductivity in the Ba-La-Cu-O System.

J. G. BEDNORZ, M. TAKASHIGE (*) AND K. A. MÜLLER

*IBM Research Division, Zurich Research Laboratory,
CH 8803 Rüschlikon, Switzerland*

(received 15 Oct 1986)

PACS. 74.70.-b

PACS. 74.10.+v

PACS. 74.70.Nr

Abstract. — The susceptibility of ceramic samples in the metallic Ba-La-Cu-O system has been measured as a function of temperature. This system had earlier shown characteristic sharp drops in resistivity at low temperatures. It has been found that the susceptibility for small magnetic fields of less than 0.1 Tesla becomes diamagnetic at somewhat lower temperatures than the resistivity drop. The highest-temperature diamagnetic shift occurs at 33 ± 2 K, and may be related to shielding currents at the onset of percolative superconductivity. The diamagnetic susceptibility can be suppressed with external fields of 1 to 5 Tesla.

October 10, 1986

(*) Permanent address: Institute for Solid State Physics, The University of Tokyo, Roppongi, Minatoku, Tokyo 106, Japan

In a recent search for high T_c superconductivity, BEDNORZ and MÜLLER [1] reported resistivity measurements in the Ba-La-Cu-O (Balacuo) system. This system was chosen because it exhibits a number of phases with mixed-valent copper constituents which exhibit itinerant electronic states between non-Jahn-Teller (J-T) Cu^{3+} and J-T Cu^{2+} ions. The existence of Jahn-Teller polarons in conducting crystals was postulated theoretically by HOECK *et al.* [2]. In general, polarons have large electron-phonon interactions, and therefore are favourable to the occurrence of high- T_c superconductivity [3].

Upon cooling Balacuo samples, first a linear metal-like decrease in resistivity is measured, followed by an approximately logarithmic increase which was interpreted as the beginning of localization [1]. On further cooling samples of certain compositions and heat treatments, an abrupt decrease by up to three orders of magnitude was observed, reminiscent of the onset of percolative superconductivity. Possible 2D superconductivity fluctuations might also be present [1], because one of the three phases in the system is of the layer-like K_2NiF_4 type, i.e., it has the $\text{La}_{2-x}\text{Ba}_x\text{CuO}_{4-y}$ composition with $1 \gg x$, $y \geq 0$. The other two phases present are the nonconducting CuO and a nearly-cubic perovskite compound. To corroborate the existence of superconductivity, the susceptibility of Balacuo samples with various compositions and preparation histories was measured. It was expected that below T_c , grains coupled by Josephson junctions or the proximity effect might yield diamagnetic shielding currents and thus cause a change from Pauli paramagnetic to diamagnetic susceptibility [4]. The experiments described below have indeed borne out this property in that a

change of sign in susceptibility occurs slightly below the onset of the resistivity drop for all samples showing a drop.

The preparation of our oxygen-deficient compounds was detailed earlier [1]. In that case, the (La,Ba):Cu ratio in the starting composition was adjusted to be 1:1. Recently, our preparations have been extended to a series with (La,Ba):Cu ratios of 2:1, which is the composition of one of the components occurring in the original 1:1 series, namely, $\text{La}_2\text{CuO}_4\cdot\text{Ba}$. Samples with varying BaO contents x were measured in the two series. Figures 1 and 2 display the resistivity of three typical representatives. The first with nominal $x = 0.06$ and 1:1 clearly shows the onset to a localization transition. The second with $x = 0.6$ at 2:1 has a resistivity drop starting at 26 K, and in the third, $x = 0.15$ and 1:1, the drop occurs at the very high temperature of $T = 35$ K (fig. 2). Table I summarizes the details of the composition and firing temperatures of the three samples. A higher annealing temperature is allowed in the 2:1 series because in the absence of excess CuO, the melting point of these mixtures is increased.

The susceptibility of the samples was measured with a newly-installed BTI (Biomagnetic Technology Inc.) variable-temperature susceptometer VTS 905. Sample weights ranged between 0.16 and 0.36 gram, see Table I. Figure 1 displays the susceptibility of sample 1, and fig. 3 those of samples 2 and 3, all measured at 0.03 T. Each of them shows Pauli paramagnetic susceptibility at higher temperatures. In sample 1, with no drop in resistivity, this metallic susceptibility persists towards 20 K with Curie-Weiss enhancement starting there. However, samples 2 and 3 exhibit changes of χ to diamagnetism on cooling. This occurs several degrees below the onset of the resistivity drop

as indicated by arrows in figs. 2 and 3. When the measuring magnetic field is increased, the diamagnetism is progressively reduced. Figure 4 reproduces such an experiment for sample 2. The inset gives the diamagnetic quenching at $T = 10$ K.

The behaviour of sample 1 is very remarkable in itself. The resistivity increases over an order of magnitude from 100 K down to 4.2 K, i.e., localization sets in, possibly owing to Jahn-Teller polarons [3]. The susceptibility is nearly constant and Pauli-like positive in the range 100 to 20 K. This is what ANDERSON predicted to occur for quasi-localized, weakly-correlated ($U \simeq 0$) $s = 1/2$ particles in disordered solids, and termed a Fermi glass [5]. First evidence of a Fermi glass resulted from electron spin resonance in the H-doped CaV_2O_6 whose conductivity followed Mott's law of variable range hopping for random systems [6]. In the present case, the temperature-independent susceptibility is followed in the same range as in $\text{CaV}_2\text{O}_6\text{:H}$. The Curie-Weiss behaviour at low temperature can originate from localized spins as in the $\text{Li}_{1+x}\text{Ti}_{2-x}\text{O}_4$ spinel system [7]. Of course, it is important to well characterize the ceramic samples under study. This has been done recently with X-ray powder diffractometry by BEDNORZ *et al.* [8]. The three phases in the 1:1 series are the nonconducting CuO , the $\text{La}_2\text{CuO}_4\text{:Ba}$, and $\text{LaCuO}_{3-y}\text{:Ba}$. The latter two, occurring in the 2:1 series only, are metallic conductors at high temperatures in the absence of Ba. LaCuO_{3-y} is a metal like LaNiO_3 [9], and so is $\text{La}_2\text{CuO}_{4-y}$ [10]. The presence of the latter phases has now also been confirmed by X-ray crystal precession measurements [8]. Obviously, random doping with Ba^{2+} causes localization in at least one metallic phase.

The onset of diamagnetism or its absence is systematic with respect to the resistivity behaviour, as figs. 1, 2 and 3 demonstrate. This is what one will expect if superconductivity with shielding currents exists. The statistical distribution of grain sizes is not known, nor is a possible variation in T_c 's. The diamagnetic shift starts *below* what presumably is the highest superconducting T_c in a sample. Theories [4] on percolative superconductors yield such a behaviour. The diamagnetism in the superconducting layer compounds of TaSe₃ and NbSe₃ is qualitatively similar to our observations, but occurs quantitatively at quite different temperatures and fields [11]. It results from superconducting loops in the percolating network, and has been the subject of calculations where the diamagnetic χ is predicted to diverge at T_c as $-\chi = A[p_c - p/p_c]^{-b}$ with the most recent results of $b = 1.29$ in two, and $b = 0.34$ in three dimensions [4]. Therefore, $-\chi$ in principle allows determining the dimensionality of a system. In our measurements, $-\chi(T)$ is rounded at the onset. The most probable reason is a distribution in T_c 's of the various grains, owing to an inhomogeneous Ba content. This requires a folding of the known analytic form of $-\chi(T)$ for a given T_c with the probability of different T_c 's. More homogeneous samples may be obtained in the future. Although neither of these efforts has been carried out, the very fact of diamagnetism considerably supports the existence of superconductivity. This diamagnetism can be suppressed by application of high external magnetic fields. The Josephson or proximity junctions then become normal, and therefore interrupt the supercurrents. The result of fig. 4 gives evidence for this. From

the inset, one sees that there is no peak in the susceptibility as it is found at H_{c1} in a single crystal, which is not expected to occur here, either.

The other two known oxide superconductors, the $\text{Li}_{1+x}\text{Ti}_{2-x}\text{O}_4$ spinel [7,12] and the $\text{BaPb}_{1-x}\text{Bi}_x\text{O}_{3-y}$ perovskite [13], have T_c 's near 11 and 13 K, respectively, quite lower than those probably found in the Balacuo. In the Li-Ti spinel, quite a clear Meissner effect, as in single crystals, has been reported for very small fields. We know of no reports on diamagnetism in $\text{BaPb}_{1-x}\text{Bi}_x\text{O}_{3-y}$. In our case, the diamagnetic shift is present, and reflects, as discussed above, the percolative character in our samples. From the onset in sample 3, this compound would become superconducting at 33 ± 2 K.

The correlation between the onset of diamagnetic shifts and drop in resistivity in all Balacuo samples measured considerably increases the likelihood for the occurrence of superconductivity. If true, it is the system with the highest T_c 's reported in any solid. The phase in which the probable superconductivity occurs is now identified as $\text{La}_2\text{CuO}_{4-y}:\text{Ba}$ [8] and an effort to grow single crystals is underway. Specific-heat measurements presently planned on our ceramic samples may further confirm what the present work indicates.

* * *

The authors would like to thank Profs. W. Buckel and E. Simanek for correspondence and interest in this work.

REFERENCES

- [1] J. G. BEDNORZ and K. A. MÜLLER: *Z. Phys. B*, **64**, 189 (1986).
- [2] K. H. HÖCK, H. NICKISCH and H. THOMAS: *Helv. Phys. Acta*, **56**, 237 (1983).
- [3] B. K. CHAKRAVERTY: *J. Phys. Lett.*, **40**, L-99 (1979); *J. Phys.*, **42**, 1351 (1981).
- [4] D. R. BOWMAN and D. STROUD: *Phys. Rev. Lett.*, **52**, 299 (1984); C. EBNER and D. STROUD: *Phys. Rev. B*, **31**, 165 (1985), and references therein.
- [5] P. W. Anderson: *Comments Solid State Phys.*, **2**, 193 (1970).
- [6] K. A. MÜLLER, T. PENNEY, M. W. SHAFER and W. J. FITZPATRICK: *Phys. Rev. Lett.*, **47**, 138 (1981).
- [7] M. R. HARRISON, P. P. EDWARDS and J. B. GOODENOUGH: *Phil. Mag. B*, **52**, 679 (1985).
- [8] J. G. BEDNORZ and M. TAKASHIGE: to be submitted to *Mat. Res. Bull.*
- [9] J. B. GOODENOUGH and M. LONGO: *Magnetic and Other Properties of Oxides and Related Compounds*. In: *Landolt-Boernstein New Series*. Vol. III/4a, *Crystal and Solid State Physics*, edited by K. H. HELLWEGE and A. M. HELLWEGE, (Springer-Verlag, Berlin, Heidelberg, New York, 1970), p. 262.
- [10] C. MICHEL and B. RAVEAU: *Chim. Min.*, **21**, 407 (1984).
- ↗
check
this ref.

- [11] R. A. BUHRMAN, C. M. BASTUSCHECK, J. C. SCOTT, and J. D. KULICK, *Inhomogeneous Superconductors - 1979 (Berkeley Springs, West Virginia)*, *AIP Conf. Proc.*, **58**, edited by D. U. GUBSER, T. L. FRANCAVILLA, S. A. WOLF, and J. R. LEIBOWITZ, (AIP, New York, 1979), p. 207.
- [12] D. C. JOHNSTON, H. PRAKASH, W. H. ZACHARIASEN, R. VISWANATHAN: *Mat. Res. Bull.*, **8**, 777 (1973).
- [13] A. W. SLEIGHT, J. L. GILLSON and P. E. BIERSTEDT: *Solid State Commun*, **17**, 27 (1975).

TABLE CAPTION

TABLE I. — *Chemical composition, firing conditions, and sample weight for susceptibility measurements.*

TABLE I

Sample	(La,Ba):Cu	Nominal composition Ba/La	Chemical analysis Ba	Firing temperature °C	Sample weight χ -measurements g
1	1:1	0.06/0.94	0.01	900	0.355
2	2:1	0.6/1.4	0.12	1300	0.164
3	1:1	0.15/0.85	0.05	900	0.330

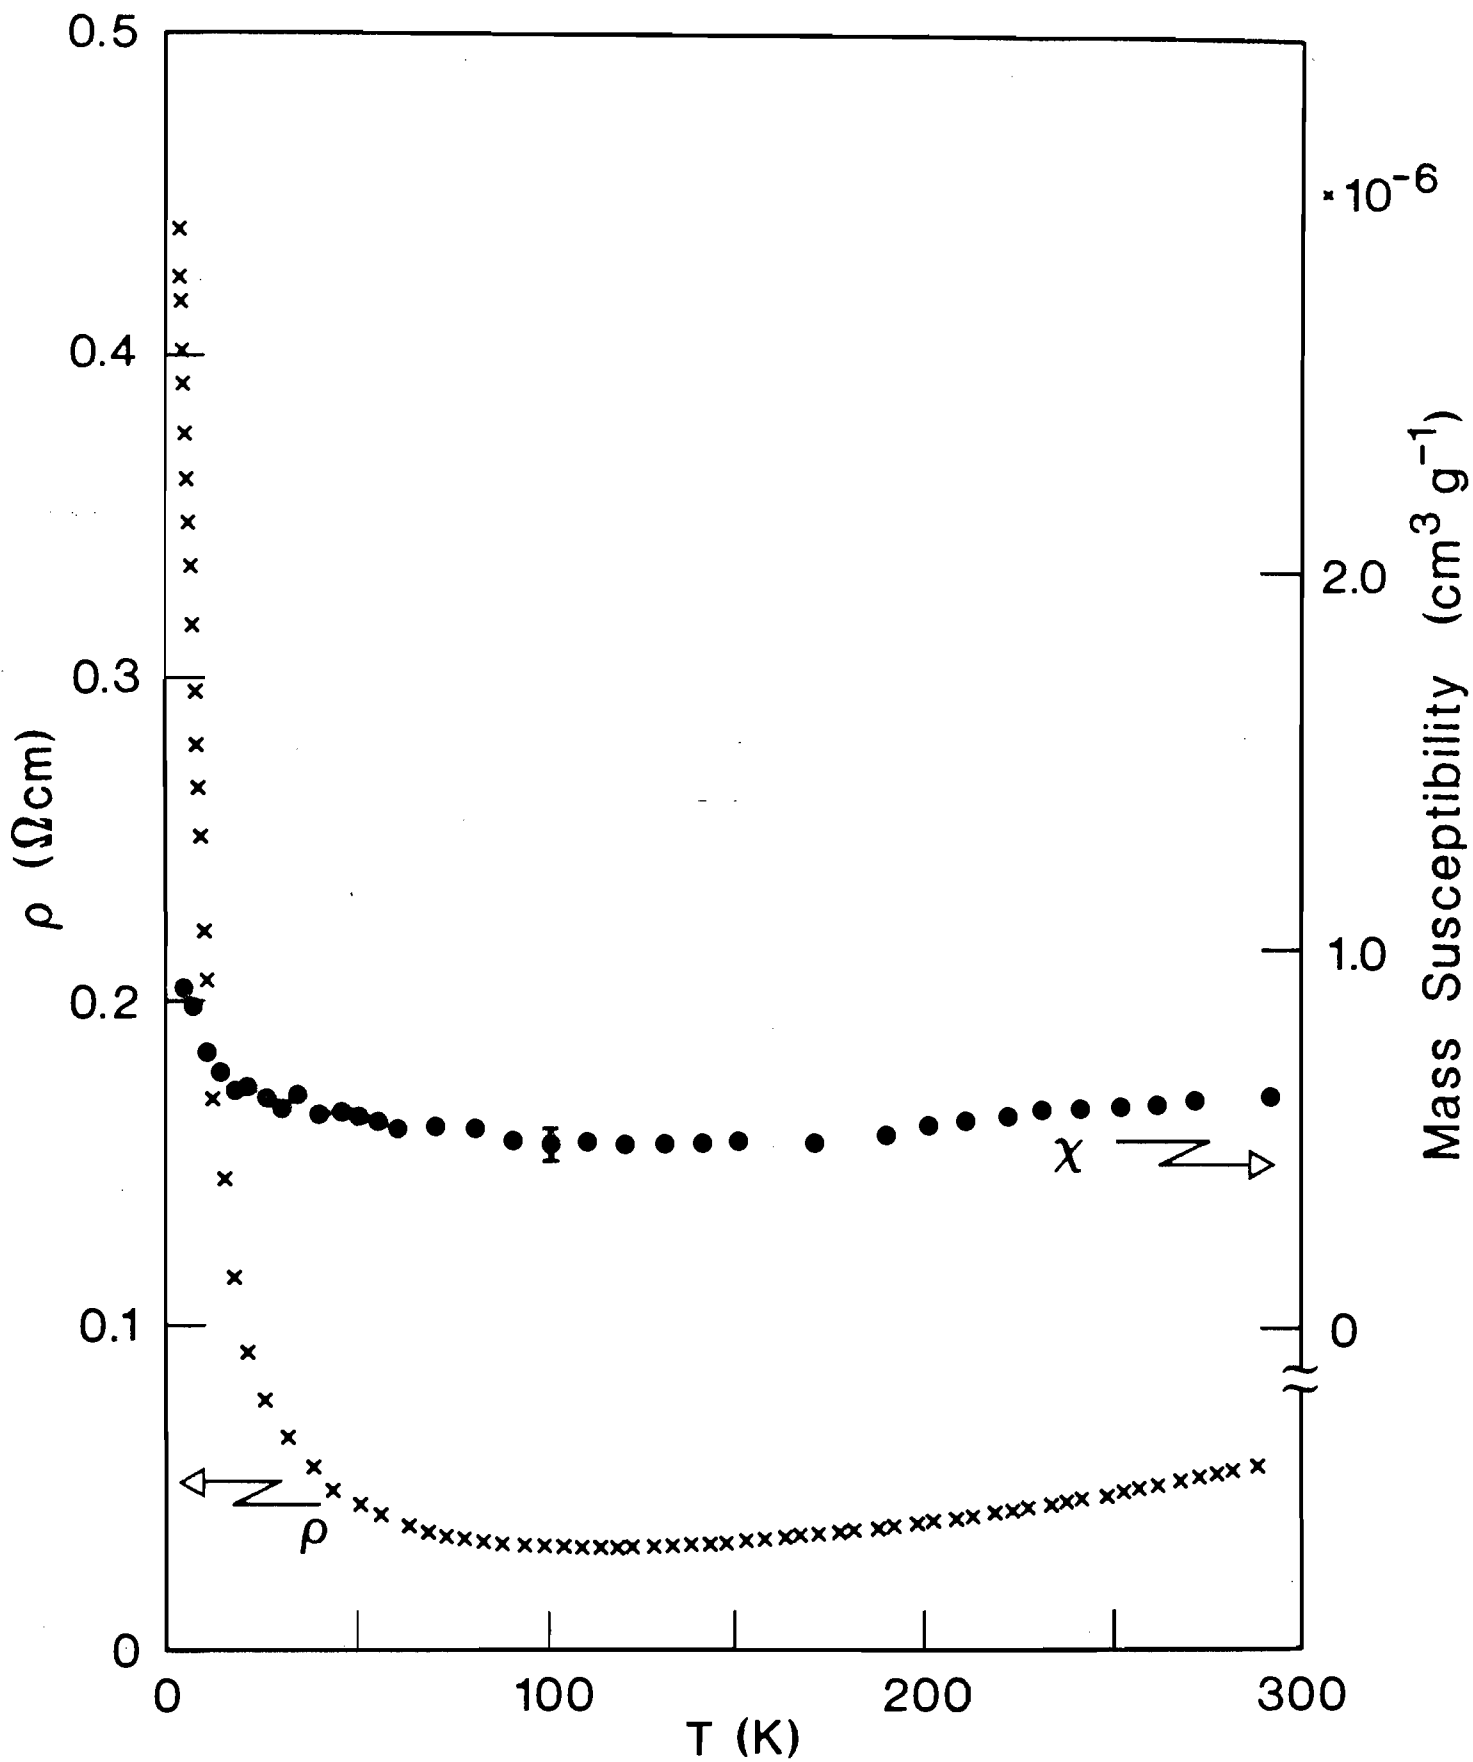


FIGURE CAPTIONS

Fig. 1. — Temperature dependence of resistivity (\times) and mass susceptibility (\bullet) of sample 1.

Fig. 2. — Low-temperature resistivity of samples 2 (\bullet) and 3 (\circ). The onset of the resistivity drop is marked by vertical arrows. Temperature determined with a calibrated Silicon Diode Sensor (DT-500, Lake Shore Cryotronics, Inc.).

Fig. 3. — Low-temperature susceptibility of samples 2 (\bullet) and 3 (\circ). Arrows indicate the temperature of the paramagnetic-to-diamagnetic transition. Temperature determined with a Rh/Fe thermometer calibrated "*in situ*" against Pt and Ge standard thermometers.

Fig. 4. — Low-temperature susceptibility of sample 2 recorded for different external magnetic fields. The inset shows the field dependence of the magnetic moment at 10 K (sample weight at 0.164 gram).

